

SiC and ZrO₂ Weigh Percentage Effects on Microstructure of Al Based Matrix Composite Fabricated by Spark Plasma Sintering Method

Meysam Toosian, Farzan Barati*, Jamshid Neamati

Department of mechanics, Faculty of engineering, Hamedan branch, Islamic azad university, Hamedan, Iran

Abstract— SiC and ZrO₂ particle are successfully reaction synthesized from powder of Al, ZrO₂ and SiC using spark plasma sintering method. The XRD of sintered composite and microstructure of the sintered products. With the ZrO₂ content increasing, the grains are remarkably refined and the ZrO₂ and nano SiC particles are dispersing more uniformly in Al matrix, forming a homogeneous structure with the least porosity.

Keywords— Aluminum, Aluminum matrix composite, zirconium, spark plasma sintering, silicon carbide.

I. INTRODUCTION

Metal matrix Composites (MMS) have a lot of application in several industries[1]. A large number of studies have been carried out by several researchers because of their unique properties [2]. Metal matrix Composite are composed from a Metal matrix phase and had phase as a reinforcement. Among metal matrix composites, AL matrix composite are one of the most applicable MMC in industries such as automobile, aerospace, transformation and military industry recently, the nanosize particulates still under consideration Aluminum and its alloys are very attractive, powder metallurgy because of eutectic phase formation with low melting point [3-4].

Moreover aluminum melting point is sufficient to be used as a matrix phase [5-6].

Among various types of reinforcement, both SiC and ZrO₂ are widely used because of their very good properties. For example, silicon carbide has high elastic modulus, high strength, excellent thermal resistance, good corrosion resistance, very good compact abrasion aluminum matrix phase low cost and its availability[7-12].

Spark plasma sintering (SPS) is a new and novel sintering process which includes high pulsed direct current and uniaxial pressure simultaneously in order to consolidate the materials. The SPS technique has high heating and cooling rates and the pressing time is also very fast [9-13].

Silicon carbide with very appropriate mechanical properties and good compatibility with AL and its alloys in one of the best additives as a reinforcement phase.

Jenix rina et al, compared the properties of AL- MMC reinforced by Zr at four different amounts of volume fraction and showed that Zr particle dispersion is uniform and the Zr phase can strengthen the matrix phase[14].

Ozben et al investigated the mechanical and machinability properties of SiC particle reinforced AL-MMC. Results showed that as the reinforcement ratio increased, the strength, hardness increases so [15].

In the present study, SPS method was employed in order to produce nano AL- MMC with SiC and ZrO₂ reinforcement phase. Finally the effects of reinforcement phase on bending strength were investigated.

II. SPARK PLASMA SINTERING

Spark plasma sintering method is a very novel powder densification technology recently.

Spark plasma sintering can be used for synthesis and processing of ceramics, metals and intermetallics; SPS method can be compared with the conventional hot pressing technology.

Also, high density current pulses at low voltage are applied directly to the powder and the pressing tool. This mechanism is used to generate a spark discharge and rapid Joule heating between particles of powder.

The fast local increase of temperature and pressure promotes the elimination of adsorbed gas and breaks the oxide layer on the surface of metal particles. Spark plasma sintering method has some advantages such as rapid heating rate and short holding time.

With considering surface activation effect, sintered bodies with meta-stable microstructures in nano sized grains can be achieved.

III. EXPERIMENTAL PROCEDURE

3.1. Materials

For the preparation of the current MMC, AL and zirconia powder with more than 99% purity and silicon carbide powder with 20 nm average size and purity of more than 98% were used as initial materials. In order to fabricate metal matrix composites these powders were mixed based on weight ratio as shown in table 1.

Table 1: weigh percentage of initial material powder.

code	AL (%)	SiC (%)	ZrO ₂ (%)
1	100	0	0
2	96	2	2
3	94	2	4
4	94	4	2
5	92	4	4
6	92	2	6

In order to obtain homogeneous composite alloys, the mixture was atomized by a plasma rotating electrode process under argon atmosphere with pressure of 40 Mpa. In the present research work the (SPS 20T-10 china) spark plasma device with 40 Mpa pressure, 480°C sintering temperature at 10 Mpa vacuum state and 6 minute holding time were carried out. At the end of holding time, the applied current was swrched off and the sample were kept inside the chamber and cooled to room temperature. The density of the sintered compacts was measured with the Archimedes method, then the specimens were metallographically prepared in the usual, thoroughly cleaned with alcohol and then dried with a hot air blower. Micro structural characterization of the sintered composited was performed using Ziess TEM.

IV. RESULTS AND DISCUSSIONS

4.1. Density

The density of sintered composites were shown at table 2. It in worthy to know that all sintered composites have more than 97 percent relative density and at the worst state, porosity in less than 0.99%. these results shows that the selected sintered temperature in proper.

Table 2: relative density and prosiry percentage of sintered composites

Samples	Relative density (%)	Porosiry (%)
1	99.8	0.02
2	98.6	0.09
3	97.9	0.14
4	96.6	0.20
5	97	0.12
6	97.3	0.11

4.2. XRD pattern of sintered composites

Figure 1 show XRD pattern for pure AL. Show in figure 1 there in not no identified peak that in not related to pure AL.

IT in worthy to know that the in XRD shows that no oxidation has been occurred during sintering process.

XRD pattern of sample 6 (%92 Al, %2 SiC, %6 ZrO₂) in showed at figure 2. IT in clear that no oxidation were take placed during sintering procedure.

XRD pattern of samples 2,3,4 and 5 are illustrated at figure 3 and the some results were obtained as illustrated for sample 1 and sample 6.

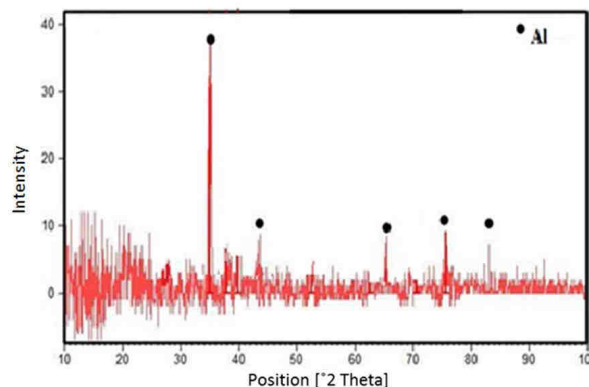


Fig.1: XRD pattern for pure Al

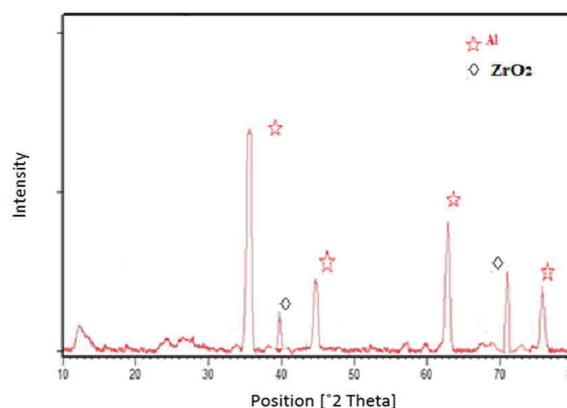


Fig.2: XRD pattern for sintered composite (%92 Al, %2 SiC, %6ZrO₂)

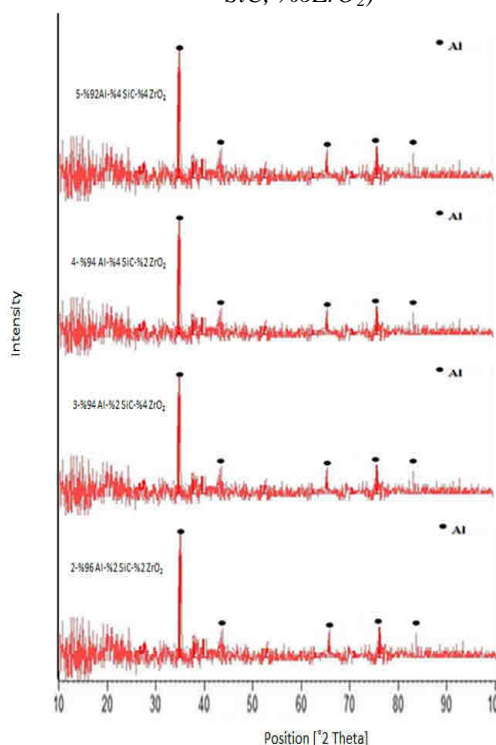


Figure 3. sintered composite XRD pattern for different additive weigh percentage

4.3. Microstructure results

The microstructure of SPS samples show a homogeneous distribution of small pores with a maximum diameter of 0.2 μm for AL sintered. As shown in figure 4, SEM microstructure Image for sintered AL 1 sample illustrate that this homogeneous distribution can be as a result of proper sintering temperature. Figure 5 shows the typical microstructures of sintered composites for different SiC and ZrO₂ weigh percentage. Figure 5 show homogeneous microstructure for sintered composites. In addition , with the ZrO₂ content increasing, the structure of the sintered composites becomes finer with remarkably refined grains of the composites with ZrO₂ and SiC particles remaining on the ground boundaries . From a comprehensive observation of the microstructures, there are pores that existed, which quantitatively decrease with ZrO₂ content increasing.

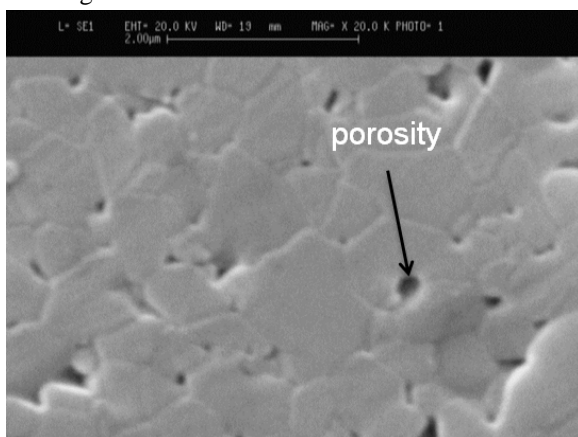


Fig.4: SEM Image for sintered pure Al.



Fig.5. SEM Image for sintered composite %94 Al-%2 SiC-%4 ZrO₂

V. CONCLUSION

Al / Sic / ZrO₂ compositor can be produced from the powder mixture of Al, SiC and ZrO₂ by way of spark plasma sintering method. By using SEM and XRD Image following results were obtained

- 1- ZrO₂ and SiC particle disperse on the grain boundaries and play a demand rate fore qroaing the matrix phase.
- 2- using SPS method leads to homogeneous structure with

relatively nonporous structure.

- 3- Rapid sintering mechanism makes no chance fore particle growth, therefore high density and low porosity percentage composites were obtained.

- 4- XRD Image show that no oxidation and phase decomposition accrued during sintering process.

REFERENCES

- [1] Cocen U., Onel k., "Failure Criteria in Fibr Reinforced - Polymer Composites", *journal Composite Science and Technology*, Volume. 62, 2002, pp.275-283
- [2] Callister W, Rethwisch D, "Fundamentals of Materials Science and Engineering", Wiley, USA, 2008, 608-610, 618-620.
- [3] Slipenyuk A, Kuprin V, Milman Yu, Spowart JE, Miracle DB. "The effect of matrix to reinforcement particle size ratio (PSR) on the microstructure and mechanical properties of a P/M processed AlCuMn/SiCp MMC". *Mater Sci Eng A* 2004;381:165-70.
- [4] Kumai S, Hu J, Higo Y, Nunomura S. "Effects of dendrite cell size and particle distribution on the near-threshold fatigue crack growth behaviour of cast Al- SiCp composites". *Acta Mater* 1996;44:2249-57.
- [5] Baccino R, Moret F. "Numerical modeling of powder metallurgy processes." *Mater Design* 2000;21:359-64.
- [6] Y.M. Youssef, R.J. Dashwood, P.D. Lee, "Effect of clustering on particle pushing and solidification behavior in TiB₂ reinforced aluminium PMMCs", *Composites: Part A* 36 (2005) 747-763.
- [7] K. Rajeswari, U. S. Hareesh, R. Subasri, Dibyendu Chakravarty, R. Johnson, " Comparative Evaluation of Spark Plasma (SPS), Microwave (MWS), Two stage sintering (TSS) and Conventional Sintering (CRH) on the densification and Micro structural Evolution of fully Stabilized Zirconia Ceramics", *Science of Sintering*, 42 (2010) 259-267.
- [8] Dongming Liu et al, "Spark Plasma Sintering of Nanostructured Aluminum: Influence of Tooling Material on Microstructure", *METALLURGICAL AND MATERIALS TRANSACTIONS A*, VOLUME 44A, APRIL 2013, 1908-1916.
- [9] Olivier Guillon, Jesus Gonzalez-Julian, Benjamin Dargatz, Tobias Kessel, Gabi Schierning, Jan Räthel, Mathias Herrmann, " Field-Assisted Sintering Technology/Spark Plasma Sintering: Mechanisms, Materials, and Technology Developments", *Advanced Engineering Materials*, Volume 16, Issue 7, pages 830-849, July 2014.
- [10] Dongming Liu et al, "Spark Plasma Sintering of Nanostructured Aluminum: Influence of Tooling

- Material on Microstructure", METALLURGICAL AND MATERIALS TRANSACTIONS A, VOLUME 44A, APRIL 2013, 1908-1916.
- [11] Hansang Kwon , Dae Hoon Park , Yongha Park , Jean François Silvain , Akira Kawasaki, Yongho Park, "Spark Plasma Sintering Behavior of Pure Aluminum Depending on Various Sintering Temperatures", *Met. Mater. Int.*, Vol. 16, No. 1 (2010), pp. 71~75.
- [12] Faming Zhang¹, Michael Reich, Olaf Kessler, Eberhard Burkel, "The potential of rapid cooling sparkplasma sintering for metallic materials" *Materials Today* , Volume 16, Number 5 , May 2013, 192-197.
- [13] Degischer HP. Innovative light metals: metal matrix composites and foamed aluminium. *Mater Design* 1997;18:221–6.
- [14] Ehsan Ghasali, Amirhossein Pakseresht, Fatemeh Safari-kooshali, Maryam Agheli, TouradjEbadzadeh, "Investigation on microstructure and mechanical behavior of Al–ZrB₂ composite prepared by microwave and spark plasma sintering", *Materials Science & Engineering A* 627 (2015) 27–30.
- [15] D.Ozben, F. Garbi al., " Properties of Al–Si composites synthesized by spark plasma sintering method", *Archives of Civil and Mechanical Engineering* (2015), <http://dx.doi.org/10.1016/j.acme.2015.02.004>